


Provided for non-commercial research and educational use only.
Not for reproduction or distribution or commercial use.



This article was originally published in a journal published by Elsevier, and the attached copy is provided by Elsevier for the author's benefit and for the benefit of the author's institution, for non-commercial research and educational use including without limitation use in instruction at your institution, sending it to specific colleagues that you know, and providing a copy to your institution's administrator.

All other uses, reproduction and distribution, including without limitation commercial reprints, selling or licensing copies or access, or posting on open internet sites, your personal or institution's website or repository, are prohibited. For exceptions, permission may be sought for such use through Elsevier's permissions site at:

<http://www.elsevier.com/locate/permissionusematerial>



Dielectric properties of polymer nanoparticle composites

Ta-I Yang^a, Peter Kofinas^{b,*}

^a Department of Chemical and Biomolecular Engineering, University of Maryland, College Park, MD 20742, USA

^b Fischell Department of Bioengineering, Building 090, Room 2113, University of Maryland, College Park, MD 20742-2111, USA

Received 11 October 2006; received in revised form 8 December 2006; accepted 15 December 2006

Available online 20 December 2006

Abstract

Well-dispersed high dielectric permittivity titanium dioxide (TiO₂) nanoparticles were synthesized utilizing a block copolymer as a template. The nanoparticles were confined within microphase separated domains of sulfonated styrene-*b*-(ethylene-*ran*-butylene)-*b*-styrene (S-SEBS) block copolymers. A crosslinker (vinyltrimethoxysilane) was incorporated into the block copolymer matrices in order to decrease the dielectric loss from the free sulfonic acid groups. Dynamic mechanical analysis experiments confirmed that nanoparticles and crosslinker were confined within the crosslinked sulfonated styrene blocks and had no effect on the chain relaxation behavior of [ethylene-*ran*-butylene] blocks. Dielectric experiments showed that higher permittivity composites can thus be obtained with a significant decrease in loss $\tan \delta$ (<0.01) when crosslinked with vinyltrimethoxysilane.

© 2006 Elsevier Ltd. All rights reserved.

Keywords: Block copolymer; Permittivity; Titanium dioxide

1. Introduction

High dielectric permittivity (ϵ) polymer-based shape forming composites have potential for applications in microwave communication devices [1], artificial muscles [2], and embedded capacitors for microelectromechanical systems [3,4]. Weight, shape-flexibility, cost effectiveness and good processability of the material are also the key factors for these applications, which is the main reason why many research efforts utilize polymeric composites. The most common process for enhancing the dielectric permittivity of a polymer is to disperse a high dielectric permittivity insulating ceramic powder such as barium titanate (BaTiO₃) [3,5,6] and lead titanate (PbTiO₃) [7] into the polymers to form composites. In order to obtain a high value of dielectric permittivity, large amount of fillers has to be loaded, resulting in loss of flexibility and inhomogeneous composites. Another approach to

obtain high dielectric permittivity composites is to utilize conductive fillers (near their percolation threshold) to produce the composites. By dispersing conductive particles, e.g., carbon nanofibers [5,6], silver particles [4] and copper phthalocyanine oligomers [2,8] into a polymer matrix, it has been demonstrated that the dielectric permittivity of the polymer significantly increases. The increased dielectric permittivity observed in such composites arises from conducting particles isolated by very thin dielectric layers to form micro-capacitors. However, the dielectric loss is very high and difficult to control, because the particles can easily form a conductive path in the composite as the filler concentration nears the percolation threshold.

The challenge to produce dielectric nanocomposites relies on the ability to manipulate the fraction, characteristic length, and arrangement of dielectric components inside the engineered composite. No systematic study to date has been published on the influence of effective volume fraction, characteristic length, and arrangement of dielectric components on the effective permittivity (ϵ) of the composites due to the intrinsic incompatibility between inorganic particles and organic matrices. Most published experiments have utilized

* Corresponding author. Tel.: +1 301 405 7335; fax: +1 301 314 6868.

E-mail address: kofinas@umd.edu (P. Kofinas).

URL: <http://www.glue.umd.edu/~kofinas>

the conventional method of blending dielectric particles into polymers, which has no real control on particle size and distribution within the polymer matrix [2–8]. However, it has been shown that the characteristic length (surface-to-volume ratio) of particles and their distribution and effective volume within the composites will significantly affect their dielectric properties [9,10]. For polymeric composites made of copper phthalocyanine, as an example, smaller particles display higher permittivity and lower dielectric loss compared to those made of larger particles [8].

The most promising way to elucidate the effect of all these factors on the dielectric properties of the composites is to make a nanocomposite, particularly with block copolymers which are well-known for their ability to template nanoparticles with narrow size distribution and uniform confinement throughout their periodic microdomains [11–13]. The use of block copolymers is shown to afford opportunities for controlling the spatial distribution and orientation of the nanocomponents. This allows much more sophisticated tailoring of the overall properties of the composite materials. The dielectric loss of a material, which limits frequency selectivity, is heavily influenced by factors such as ionic conduction and structural heterogeneities (microstructure defects or porosity), which will generate flow of charges and results in thermal dissipation of energy [14]. Block copolymer nanocomposites could significantly reduce such factors causing dielectric loss by providing insulation layers and highly periodic templated nanoparticles.

We report a novel method of producing high dielectric permittivity polymer-based composites by utilizing a block copolymer. The nature of the self-assembled nanoscale morphology of the block copolymer enables the formation of stable particles uniformly dispersed within the polymer matrix. Sulfonated [styrene-*b*-(ethylene-*ran*-butylene)-*b*-styrene] (S-SEBS) block copolymers containing sulfonic acid groups (SO_3H) were selected to investigate their ability to template nanoparticles within their self-assembled microstructures. In order to obtain high dielectric permittivity particles, organic complexes of titanium were selected to form titanium dioxide (TiO_2) nanoparticles which preferentially associate with sulfonic acid groups of one of the blocks of the copolymer. Upon solvent evaporation and film casting, nanoparticles are formed via a hydrolysis reaction uniformly distributed within the polymer matrix, which acts as a template to enhance the ordering of the high dielectric permittivity nanoparticles. The crosslinker (vinyltrimethoxysilane) was also incorporated into S-SEBS block copolymers to study its effect on dielectric and mechanic properties of the composites. The composites were characterized by X-ray photoelectron spectroscopy (XPS), dynamic mechanical analysis (DMA), and dielectric analysis (DEA).

2. Experimental section

2.1. Materials

Titanium acetylacetonate (TYZOR AA105) was supplied by E.I. du Pont de Nemours and Company. Sulfonated

[styrene-*b*-(ethylene-*ran*-butylene)-*b*-styrene] (S-SEBS) block copolymer solution and vinyltrimethoxysilane were purchased from Aldrich. The molecular weight of the S-SEBS block copolymer was 80,000 g/mol consisting 29 wt% styrene blocks and 59.7 mol% of styrene blocks sulfonated. All chemicals were used as received without further purification.

2.2. S-SEBS templated titanium dioxide (TiO_2) nanoparticles

Titanium acetylacetonate was selected as the precursor to form the TiO_2 nanoparticles. The S-SEBS solutions were mixed with different concentrations of precursors, where the molar ratio between SO_3H groups of S-SEBS and Ti was 100:2, 4, 16, and 32. The solution was vigorously stirred for 30 min. The Ti organometallic complexes preferentially attached to the sulfonated styrene blocks. A solid film was formed by static casting over a period of one week. The Ti organometallic complexes attached to the SO_3H groups were gradually hydrolyzed and formed titanium oxide nanoparticles within the sulfonated styrene blocks.

2.3. S-SEBS templated titanium dioxide (TiO_2) composites with crosslinker

The procedure was the same as for synthesis of S-SEBS templated TiO_2 , except that both vinyltrimethoxysilane crosslinker and TiO_2 precursors were simultaneously added to S-SEBS polymer solutions. The molar ratio of crosslinker to SO_3H groups within the copolymer was kept at 2.5 while the molar percentage of $\text{Ti}/\text{SO}_3\text{H}$ varied from 2 to 32. The solution was vigorously stirred for 30 min, then poured into a Teflon boat. A solid film was formed by static casting over a period of one week. The resulting films were placed in an oven for heat-treatment at 150 °C for 24 h and exposed to UV light (260–320 nm) for 20 min at 150 °C.

2.4. Characterization

X-ray photoelectron spectroscopy (XPS, AXIS 165, Kratos) was used to investigate the oxidation state of titanium. The charge-shifted spectra were corrected assuming that the adventitious $\text{C}1s$ peak detected was at 284.600 eV. Dielectric measurements for the resulting S-SEBS nanocomposites were performed using a dielectric analyzer (DEA 2970, TA Instruments). The samples were sandwiched between the ceramic parallel plate sensors, and subjected to a force of 200 N. The DEA cell was purged with dry nitrogen at a flow rate of 500 mL/min for 30 min to ensure the absence of moisture during measurements. The experiments were performed at frequencies of 1, 5, 10, 22, 46, 100, 215, 464, 1000, 2150, 4640, 10,000 Hz at 35 °C. Transmission electron microscopy (TEM, HITACHI H-600) operated at 100 keV was used to observe the morphology of the composites. The samples for TEM were prepared by solvent casting directly onto a copper grid and were visualized without any staining to enhance TEM contrast. Tensile strength and ultimate elongation,

as well as storage and loss modulus transitions were studied with a dynamic mechanical analyzer (DMA Q800, TA Instruments). Thermogravimetric analysis (TGA-50, SHIMADZU) was used to investigate the thermal stability of the composite. Samples were heated at 10 °C/min under ambient conditions.

3. Results and discussion

3.1. Templated titanium dioxide (TiO_2) composite morphology

The morphologies of the nanocomposites were investigated by transmission electron microscopy (TEM). The pure S-SEBS block copolymer without any templated particles exhibited a microphase separated morphology, shown in Fig. 1. The microphase separated morphology was observed without any TEM staining. TEM contrast results from atoms of heavier atomic number. It is believed that the sulfonic acid groups (59.7 mol%) on the sulfonated styrene blocks provided the contrast (darker stripes) for the TEM image. For the S-SEBS block copolymer mixed with TiO_2 precursors, the resulting nanoparticles were confined within the darker stripes containing the sulfonated styrene blocks, as shown in Fig. 2. This experiment showed that sulfonic acid groups (SO_3H) can preferentially associate with titanium organometallic complexes (Tyzor AA105) and then template the TiO_2 nanoparticles

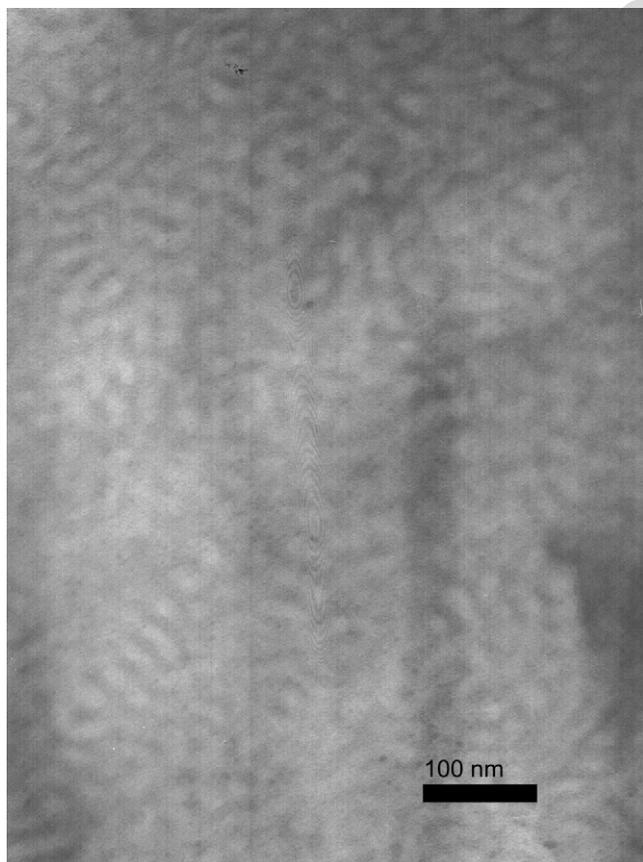


Fig. 1. TEM image of S-SEBS block copolymer.

within self-assembled microstructures of the S-SEBS block copolymers for $\text{Ti}/\text{SO}_3\text{H}$ molar ratios below 32%. High-resolution XPS was utilized to determine the oxidation state of the nanoparticles, as shown in Fig. 3. The binding energies of $\text{Ti } 2p_{1/2}$ (464.15 eV) and $2p_{3/2}$ (458.50 eV) are in agreement with existing literature and are characteristic of titanium dioxide (TiO_2) [15,16].

It has been reported that sulfonic acid groups significantly contribute to proton conductivity which leads to increase in the dielectric loss of the composite [17]. In order to reduce the dielectric loss resulting from the mobile protons in the sulfonic acid groups of S-SEBS copolymers, the crosslinking reagent vinyltrimethoxysilane was introduced into the sulfonated styrene block of S-SEBS to remove the protons of the sulfonic acid groups (SO_3H) [18,19].

The block copolymer microphase separated morphology (Fig. 4) for the S-SEBS with crosslinker (the molar ratio of crosslinker to the SO_3H groups was 5.5) showed the same morphology as the un-crosslinked S-SEBS block copolymer except that the contrast for the TEM imaging was more enhanced. The crosslinker (silane) tends to preferentially associate with SO_3H groups through hydrogen bonds and therefore enhance the contrast. In addition, the un-changed glass transition temperature of the [ethylene-*ran*-butylene] block also indicates that the crosslinker was excluded from [ethylene-*ran*-butylene] block (see Section 3.2). These experiments therefore confirmed that the crosslinker was confined within the sulfonated styrene blocks. The morphologies of the S-SEBS titanium dioxide (TiO_2) composites with crosslinker showed that the TiO_2 nanoparticles were confined within the sulfonated styrene blocks with the morphology being unaffected (domain = 15 nm) by simultaneous addition of crosslinker and TiO_2 precursors (see Fig. 5). The molar ratio of crosslinker to SO_3H groups within the copolymer was kept at 2.5 while the molar percentage of $\text{Ti}/\text{SO}_3\text{H}$ varied from 2 to 32. We have thus demonstrated that the self-assembled morphologies of block copolymers enable the formation of TiO_2 nanoparticles well-dispersed within the sulfonated styrene domains throughout the entire sample. In addition, both TiO_2 nanoparticles and crosslinks could be simultaneously formed within the sulfonated styrene block while maintaining the original block copolymer microphase separation.

3.2. Mechanical properties of TiO_2 composites with crosslinker

Dynamic mechanical experiments were used to evaluate the tensile strength and ultimate elongation of the S-SEBS composites containing titanium dioxide nanoparticles and crosslinker. Controlled force stress–strain experiments were performed to obtain the stress–strain curve shown in Fig. 6. Compared to the pure S-SEBS block copolymer, the ultimate elongation of the composites was smaller, however, the tensile strength was larger. The glass transition temperatures of the nanocomposites were determined by a controlled strain (0.1%) temperature ramp experiment (frequency set at 1 Hz and heating rate was 7 °C/min), as shown in Fig. 7. The glass transition temperature

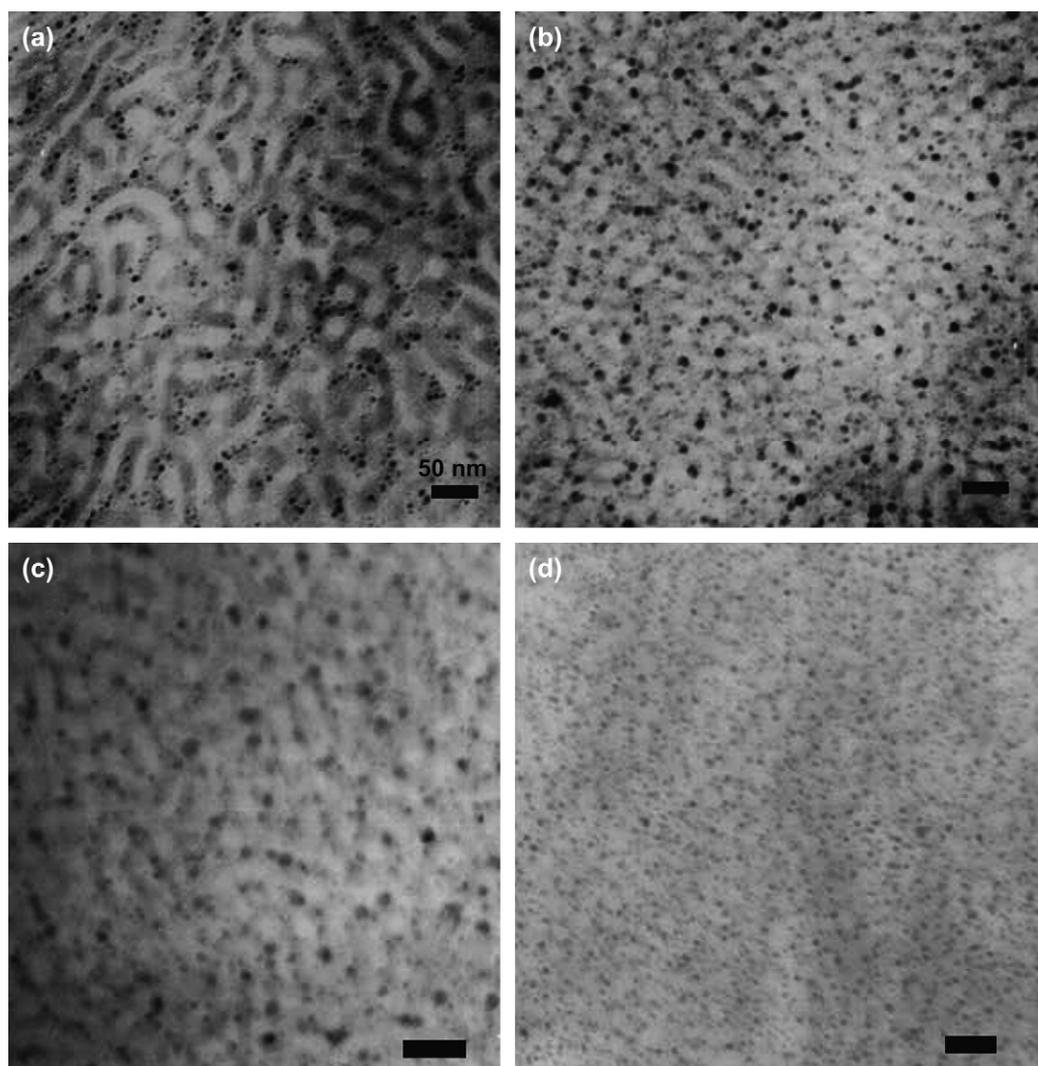


Fig. 2. TEM images of S-SEBS doped with different Ti molar concentrations: (a) 2%, (b) 4%, (c) 16%, and (d) 32% (scale bar = 50 nm).

of [ethylene-*ran*-butylene] blocks was not significantly affected by the doped TiO₂ nanoparticles and crosslinker, only shifting to 3 °C higher for all the composites. This indicated that nanoparticles and crosslinker were both confined within

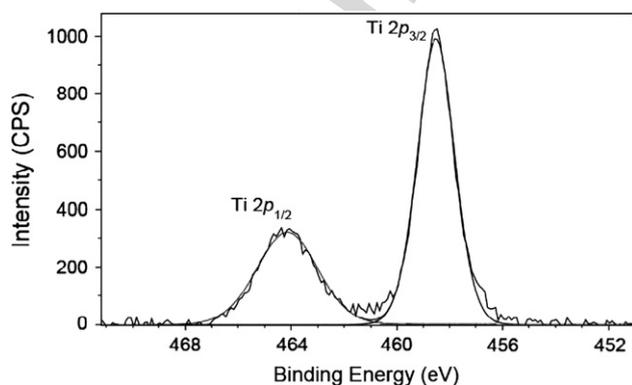


Fig. 3. XPS spectra of S-SEBS block copolymer composite with templated TiO₂ nanoparticles.

the sulfonated styrene blocks and had no effect on the chain relaxation behavior of the rubbery [ethylene-*ran*-butylene] blocks. However, upon crosslinking the glass transition temperature of the sulfonated styrene blocks was suppressed compared to the broad peak between 50 and 250 °C of the pure S-SEBS copolymer. It has been reported in literature that the relaxation peak of the composites becomes broader and shifts to higher temperatures with increasing crosslink density or addition of particles [21,22]. Since the nanocomposites consist of only up to 6.4 wt% of TiO₂ particles, the suppressed transition temperature could be attributed to the crosslinked sulfonated styrene groups resulting from addition of crosslinker (silane) and sulfone group formation. The TGA data (Fig. 8) show that the weight loss for the pure S-SEBS block copolymer was higher with increasing temperature compared to the temperature-stable S-SEBS with crosslinker (up to 300 °C). For the un-crosslinked S-SEBS, the weight loss contributes to water evaporation below 100 °C. The sulfonic acid groups are eliminated to form sulfone (RSO₂R) groups at temperatures higher than 100 °C [23–25].

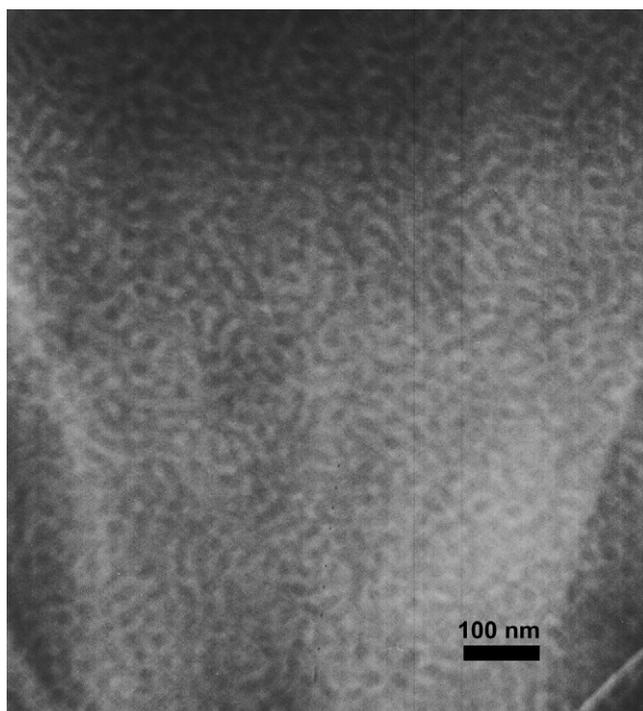


Fig. 4. TEM image of S-SEBS mixed with crosslinking agent.

The crosslinked nanocomposites containing confined TiO_2 nanoparticles also led to higher tensile strength and less ultimate elongation compared to un-crosslinked S-SEBS, as shown in Fig. 6.

3.3. Swelling tests

Swelling experiments were performed to demonstrate the absence of sulfonic acid groups in the crosslinked composites. Three different polymers were tested:

- (1) Block copolymer of [styrene-*b*-(ethylene-*ran*-butylene)-*b*-styrene] (SEBS) with 28 wt% styrene.
- (2) Block copolymer of [sulfonated styrene-*b*-(ethylene-*ran*-butylene)-*b*-styrene] (S-SEBS) with 29 wt% styrene and 59.7 mol% of styrene sulfonated.
- (3) S-SEBS block copolymer with crosslinker [molar ratio of crosslinker/ SO_3H = 2.5].

The swelling ratio (q) was calculated, as $q = W_a/W_0$, where W_a is the weight of the film swollen by water to equilibrium and W_0 is the weight after drying. The results shown in Fig. 9 demonstrate that the swelling ratio for the SEBS copolymer without any strong SO_3H polar groups was 1, which means water cannot penetrate into the polymer. In contrast, the S-SEBS block copolymer exhibited significant swelling ($q = 4$) due to the highly hydrophilic sulfonic acid groups on the sulfonated styrene blocks. For the S-SEBS block copolymer with crosslinker, the swelling ratio dropped back to 1. This experiment qualitatively indicated that the hydrophilic sulfonic acid groups were eliminated to form the sulfone

crosslinks or were replaced by the hydrophobic silane groups of the crosslinker.

3.4. Dielectric properties of S-SEBS block copolymer TiO_2 composites

The dielectric permittivity of a material is usually given relative to that of free space, and is known as relative permittivity (ϵ_r), or dielectric constant (k). The dielectric response of the nanoparticle composites at various frequencies is described in terms of the complex permittivity (ϵ^*) which is represented by its real and imaginary parts.

$$\epsilon^* = \epsilon' - i\epsilon'' \quad (1)$$

where ϵ' is the dielectric permittivity and ϵ'' is the dielectric loss. The dielectric loss tangent ($\tan \delta$) is defined as

$$\tan \delta \equiv \frac{\epsilon''}{\epsilon'} \quad (2)$$

The dielectric data obtained from the pure (un-crosslinked) S-SEBS block copolymer suggested that this polymer was a lossy material, which means that the charges dissipated are comparable to those stored within S-SEBS and not favorable for dielectric material applications. For example, the dielectric loss tangent of pure S-SEBS was 0.6 while the relative permittivity was 5258 at a frequency as of 10 kHz, as shown in Fig. 10. The reason for the prominent loss was contributed to the strong proton/charge conducting ability of the SO_3H groups on the sulfonated styrene blocks, leading to the dissipation of the charges within the S-SEBS [20]. In order to reduce the dielectric loss resulting from the mobile protons in the sulfonic acid groups, crosslinkers were introduced into the sulfonated styrene blocks to replace the protons. The resulting S-SEBS/crosslinker composite, where the molar ratio of crosslinker to SO_3H groups was 2.5, showed that the dielectric loss tangent was suppressed below 0.01 at 10 kHz as well as for the composites with various amounts of TiO_2 nanoparticles (see Fig. 11). The data also showed that dielectric loss decreased with increasing amount of nanoparticles which can be due to the strong polar SO_3H groups being replaced by the crosslinker and the mobility of polymer chains being hindered by the nanoparticles and crosslinker. The data obtained also show that the relative permittivity of the composites increases by doping TiO_2 nanoparticles: the higher the amount doped, the higher the permittivity obtained as shown in Fig. 11.

4. Conclusions

We have shown the feasibility of producing high dielectric permittivity nanoparticles (TiO_2) uniformly dispersed within polymer matrices. All nanoparticles were confined within the crosslinked sulfonated styrene blocks and no effect was observed on the phase separation behavior of the S-SEBS block copolymer. Dielectric experiments showed that higher permittivity composites can thus be obtained with a significant

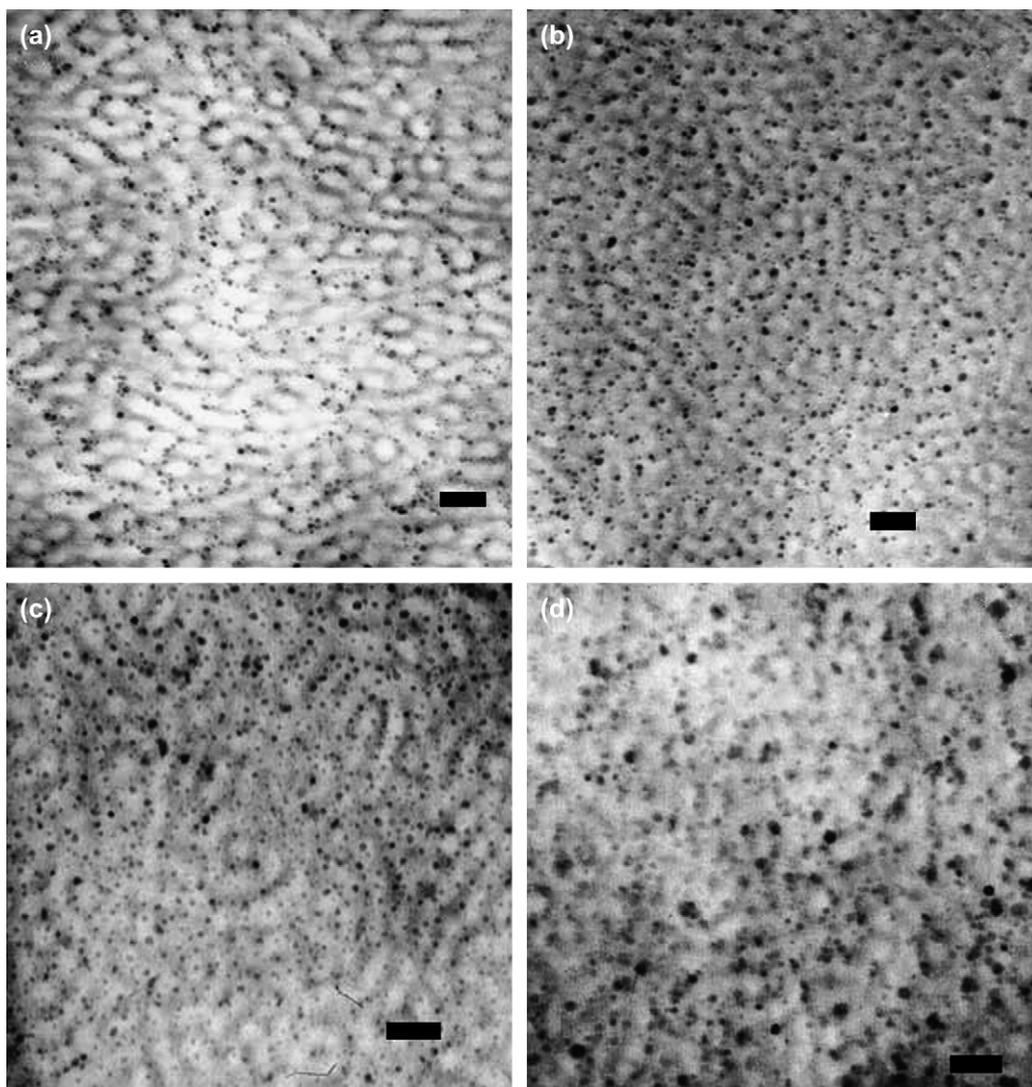


Fig. 5. TEM images of crosslinked S-SEBS doped with different Ti molar concentrations: (a) 2%, (b) 4%, (c) 16%, and (d) 32% (scale bar = 50 nm).

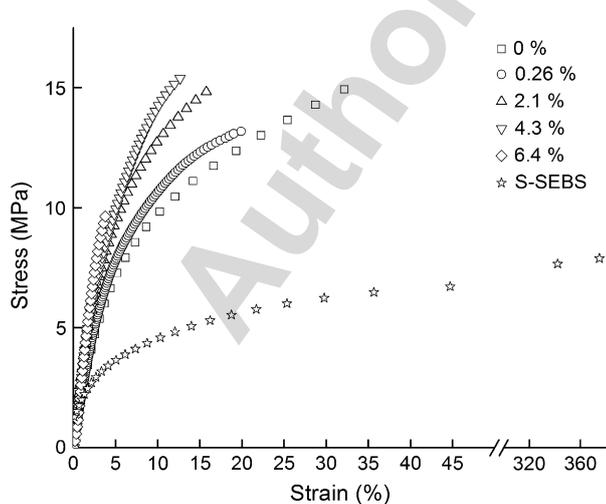


Fig. 6. Mechanical stress–strain curves of S-SEBS composites with different TiO_2 wt%. Molar ratio of crosslinker/ SO_3H = 2.5.

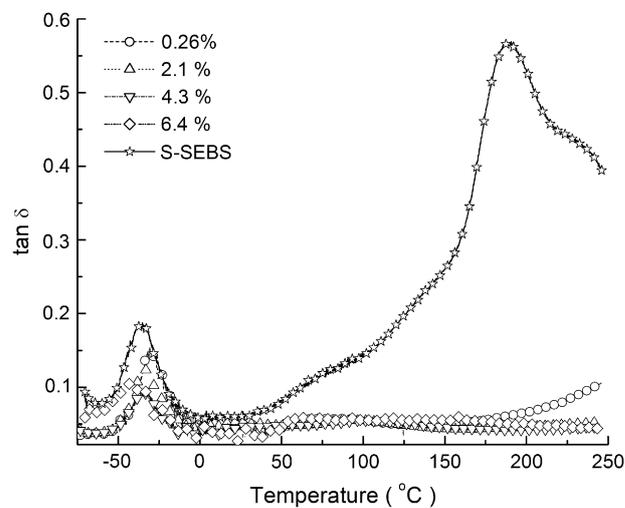


Fig. 7. Mechanical loss tangent of S-SEBS composites with different TiO_2 wt%. Molar ratio of crosslinker/ SO_3H = 2.5.

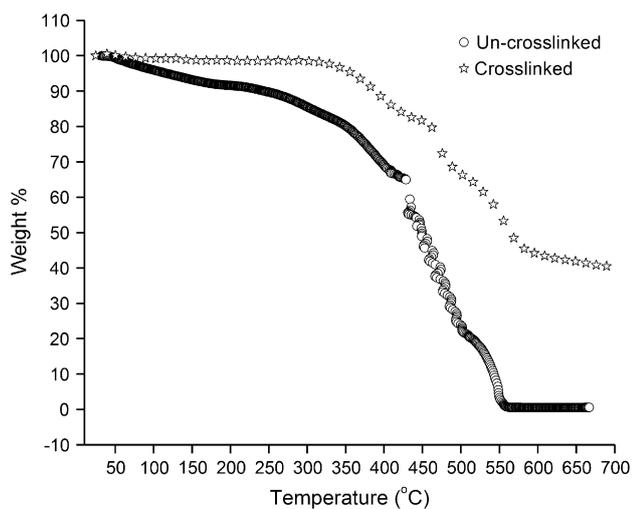


Fig. 8. TGA curves for pure S-SEBS and S-SEBS with crosslinker. Molar ratio of crosslinker/SO₃H = 2.5.

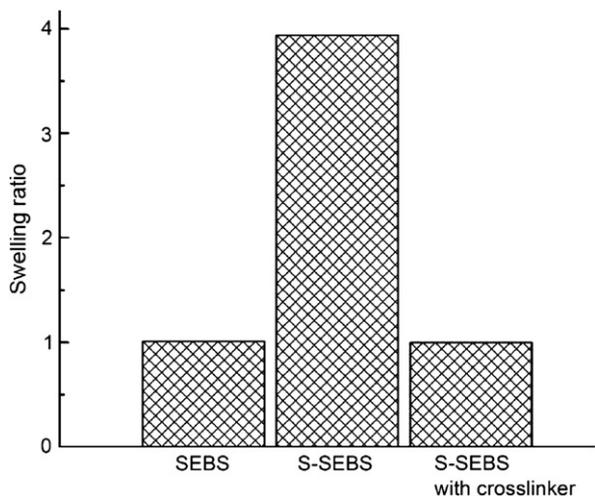


Fig. 9. Swelling ratios for various S-SEBS block copolymers.

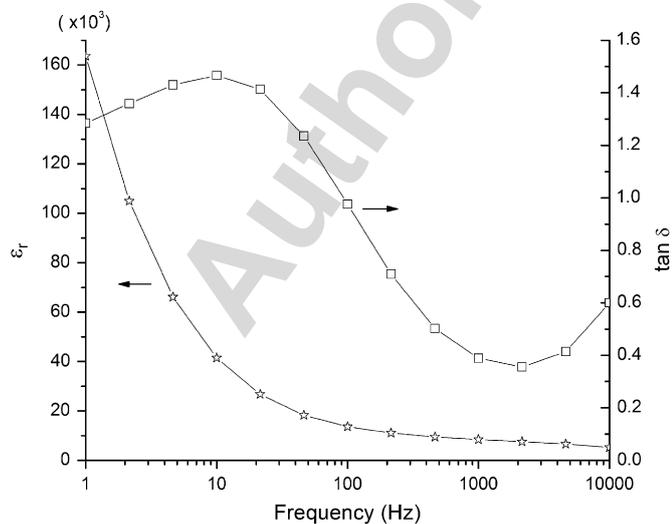


Fig. 10. Dielectric properties of un-crosslinked pure S-SEBS copolymer.

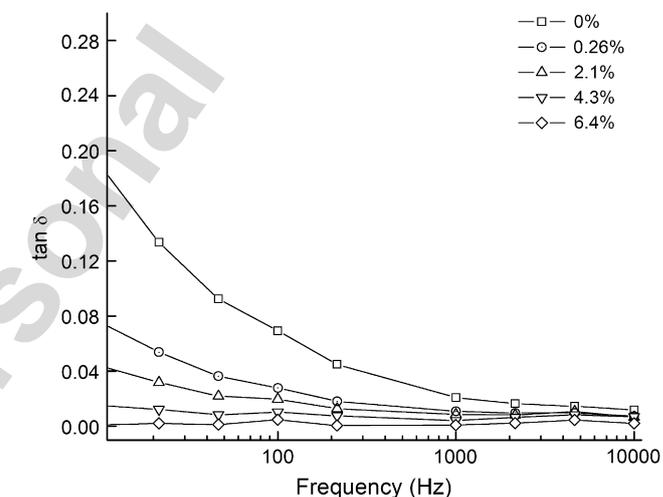
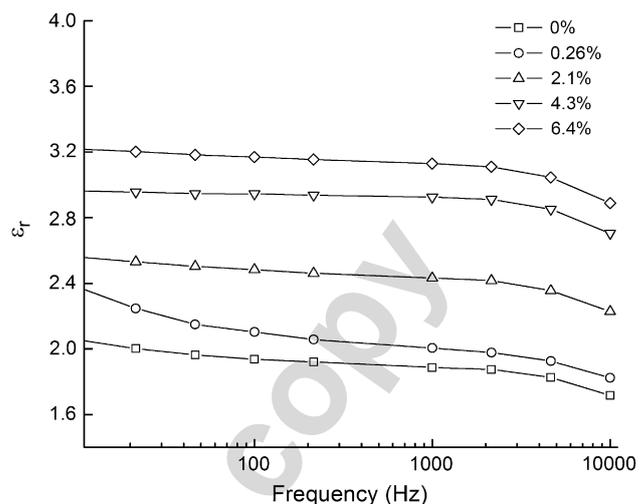


Fig. 11. Dielectric properties for S-SEBS with different TiO₂ wt%. Molar ratio of crosslinker/SO₃H = 2.5.

decrease in loss $\tan \delta$ (<0.01) when crosslinked with vinyltrimethoxysilane.

Acknowledgements

This study is based upon work supported by the National Science Foundation # DMR-0442029.

References

- [1] Vanderah TA. Science 2002;298:1182–4.
- [2] Zhang QM, Li H, Poh M, Xu H, Cheng ZY, Xia F, et al. Nature 2002;419: 284–7.
- [3] Choa SD, Lee JY, Hyuna JG, Paik KW. Mater Sci Eng B 2004;110: 233–9.
- [4] Pothukuchi S, Li Y, Wong CP. J Appl Polym Sci 2004;93:1531–8.
- [5] Dang ZM, Fan LZ, Shen Y, Nan CW. Chem Phys Lett 2003;369(1–2): 95–100.
- [6] Dang ZM, Fan LZ, Shen Y, Nan CW. Mater Sci Eng B 2003;103(2): 140–4.
- [7] Bai Y, Cheng ZY, Bharti V, Xu H, Zhang QM. Appl Phys Lett 2000; 76:3804–6.

- [8] Wang JW, Shen QD, Yang CZ, Zhang QM. *Macromolecules* 2004;37(6): 2294–8.
- [9] Nan CW. *Prog Mater Sci* 1993;37:1–116.
- [10] Tuncer E, Serdyuk YV, Gubanski SM. *IEEE T Dielect El In* 2002;9(5): 809–28.
- [11] Bockstaller MR, Mickiewicz RA, Thomas EL. *Adv Mater* 2005;17(11): 1331–49.
- [12] Förster S, Antonietti M. *Adv Mater* 1998;10(3):195–217.
- [13] Park C, Yoon J, Thomas EL. *Polymer* 2003;44:6725–60.
- [14] Williams G. Dielectric properties. In: Allen G, Bevington JC, Booth C, Price C, editors. *Comprehensive polymer science*, vol. 2. New York: Pergamon Press; 1989. p. 601–31.
- [15] Wagner CD. The NIST X-ray photoelectron spectroscopy (XPS) database. Gaithersburg, MD: U.S. Dept. of Commerce, National Institute of Standards and Technology; 1991.
- [16] Jensen H, Soloviev A, Li Z, Sogaard EG. *Appl Surf Sci* 2005;246(1–3): 239–49.
- [17] Kim B, Kim J, Jung B. *J Membr Sci* 2005;250(1–2):175–82.
- [18] Plueddemann EP. *Silane coupling agents*. 2nd ed. New York: Plenum Press; 1991 [chapter 2].
- [19] Arkles B. *MRS Bull* 2001;26(5):402–8.
- [20] Yang JE, Lee JS. *Electrochim Acta* 2004;50(2–3):617–20.
- [21] Li C, Wu J, Zhao J, Zhao D, Fan Q. *Eur Polym J* 2004;40: 1807–14.
- [22] Kalakkunnath S, Kalika DS, Lin HQ, Freeman BD. *J Polym Sci Polym Phys* 2006;44(15):2058–70.
- [23] Kucera F, Jancar J. *Polym Eng Sci* 1998;38(5):783–92.
- [24] Chen NP, Hong L. *Eur Polym J* 2001;37(5):1027–35.
- [25] Mauritz KA, Blackwell RL, Beyer FL. *Polymer* 2004;45(9): 3001–16.